

Characterization of superconducting nanometric multilayer samples for SRF applications: first evidence of magnetic screening effect

C. Z. Antoine¹, S. Berry¹, S. Bouat², J-F. Jacquot², J-C. Villegier², G. Lamura³, A Gurevich⁴

¹CEA, Irfu, SACM, Centre d'Etudes de Saclay, 91191 Gif-sur-Yvette Cedex, France

²CEA, Inac, 17 Rue des Martyrs, 38054 Grenoble-Cedex-9, France

³LAMIA, Physics Department, Genoa University Via Dodecaneso 33, 14146 Genova, Italy

⁴National High Magnetic Laboratory, Florida State University, 1800 E. Paul Dirac Dr., Tallahassee, FL 32310, USA

Best *rf* bulk niobium accelerating cavities have nearly reached their ultimate limits at *rf* equatorial magnetic field $H \approx 200$ mT close to the thermodynamic critical field H_c . In 2006 Gurevich proposed to use nanoscale layers of superconducting materials with high values of $H_c > H_c^{Nb}$ for magnetic shielding of bulk niobium to increase the breakdown magnetic field of SC *rf* cavities¹. Depositing good quality layers inside a whole cavity is rather difficult. So as a first step, characterization of single layer coating and multilayers was conducted on high quality sputtered samples by applying the technique used for the preparation of superconducting electronics circuits. The samples were characterized by X-ray reflectivity, dc resistivity (PPMS) and dc magnetization (SQUID) measurements. Dc magnetization curves of a 250 nm thick Nb film have been measured, with and without a magnetron sputtered coating of a single or multiple stack of 15 nm MgO and 25 nm NbN layers. The Nb samples with/without the coating exhibit different behaviors and clearly show an enhancement of the magnetic penetration field. Because SQUID measurements are influenced by edge and shape effects we propose to develop a specific local magnetic measurement of H_{C1} based on ac third harmonic analysis in order to reveal the true screening effect of multilayers.

INTRODUCTION

Bulk niobium cavities have proven to provide the highest accelerating gradients up to 40 MV/m in superconducting *rf* cavities for particle accelerator applications. When the accelerating field reaches this value, the magnetic field component near the equator is close to the thermodynamic critical field $H_c^{Nb} \approx 200$ mT at which the screening current density reaches the maximum depairing current density in a superconductor.

There are several evidences that the RF dissipation observed in Nb cavities at high field has a magnetic origin in which case the BCS surface resistance R_{BCS} increases at high field. As H_{RF} approaches H_c , the normal electrons density and R_{BCS} increases due to the effect of the RF current pair-breaking on thermal activation which in turn increases heating, making R_{BCS} nonlinear at high field. So far this nonlinear *rf* response has only been evaluated for type II superconductors in the clean limit and at low frequency. It shows that at high field the surface resistance $R_s(T, H_{RF})$ increases exponentially with field and temperature, and can give rise to thermal runaway [1, 2].

This model could in particular explain the hot spots observed on cavities where either surface defects or bundles of trapped vortices can produce localized dissipative regions from which heat spreads along the cavity surface over tens of mm. The magnetic/vortex origin of some of such hot spots has been recently demonstrated [3].

The necessity to prevent strong RF dissipation due to vortex penetration at high fields has resulted in the monopoly of niobium in SRF applications since the clean Nb has the highest value of the lower critical field $H_{C1} \approx 180$ mT at 0 K among all superconductors. Attempts to

use higher T_C and H_{C2} superconductors have failed so far, probably due to their low H_{C1} , that allows early penetration of magnetic vortices resulting in high surface dissipation (for a recent review on that topic see [4]).

MULTILAYERS

The use of composite structures comprised of nanoscale multilayers of superconducting materials with $H_C \gg H_{NbC}$ for magnetic shielding of niobium cavities has been proposed to significantly increase the breakdown field in *rf* accelerating applications [5].

Very high H_{C1} can indeed be achieved with films whose thickness d is smaller than the magnetic penetration depth λ , in a configuration where the field is parallel to the surface of the film [5]. So such films could be used to screen bulk niobium and allow much higher field to be reached inside the cavities. Bulk niobium is still necessary to prevent perpendicular vortices to penetrate the film and dielectric layers are needed to prevent Josephson coupling between coating layers and Nb substrate. Such structures would be particularly efficient in the case of *rf* elliptic cavities where the magnetic field is confined in the cavity and is parallel to its surface.

Deposition techniques

Thin film deposition on curved, large surfaces like the cavities is difficult as it has been shown recently (see e.g. [6]). Thus, we are searching for a deposition technique which can then be developed for cavity geometries to provide uniform coating of nano-layers, with sharp interfaces, low densities of defects, including grain boundaries and impurities, and low residual stress. Testing such nano-structures deposited inside cavities would be fairly easy since in this field configuration no side effects are expected.

As a first step we have prepared high quality samples and characterized those using standard measurements. Several deposition techniques can achieve very good quality films in specific conditions, but their characterization using classical dc techniques cannot be unambiguously extrapolated to predict the *rf* behavior of the film coating in a cavity. Nevertheless, demonstrating the effective screening effect of nanometer scale NbN films (high H_{c1}) on good Nb samples could initiate the interest of scientific community in searching alternative deposition techniques like the one presented in [7, 8]. To reach this goal, the evaluation of the first penetration field for layered samples as compared to the bulk niobium is of fundamental importance.

In order to produce high quality layered films, we applied the magnetron sputtering technique; an asserted technique well developed for the preparation of superconducting electronics circuits particularly for Josephson junctions and detectors fabrication.

EXPERIMENTAL DETAILS

We have grown one 25 nm single NbN layer (SL), and one multilayer (ML) with four 12 nm NbN layers deposited on a 250 nm Nb layer. The intermediate dielectric layer was MgO (all parameters of the samples are listed in Table 1) NbN was deposited by dc magnetron sputtering from a 6-inches diameter niobium target in a reactive (nitrogen/argon) gas mixture at 300°C. The same target is used for Nb deposition applying only argon pressure, whereas the MgO layer is *rf*-magnetron sputtered from an MgO target. More details on the technique can be found in [9]. The NbN top layer is further RIE etched on a part of the wafer to provide the bulk niobium reference sample (Ref).

X-ray characterization

High angle X-rays Diffraction measurements provide information about the crystalline relations between the substrate and the deposited layers. For instance, for sample SL we observed that Nb, NbN, and MgO were all (200) textured at 100% although it was not possible to determine if they were polycrystalline or monocrystalline. In addition the NbN layer was slightly expanded (0.5%) in the (200) direction. For sample ML we observed also a (200) texture for each layer, but the (200) Nb texture is only partial (~ 89 %).

Low angle X-rays reflectivity gave information about thicknesses and interface roughness of the different layers. The measured signal was fitted using Paratt formalism that takes into account the existence of several layers of various electronic densities [10]. The resulting data are summarized in table 1.

Table 1 : summary of the X-rays reflectivity analysis

Sample	Thickness (nm)	Roughness (nm)	Sample	Thickness (nm)	Roughness (nm)
Nb	250	1	Nb	250	1
MgO	14	1	MgO	15	1
NbN	25	1.5	NbN	12	1.5

* Sample ML has 4 NbN/MgO layers of the same thickness

T_c measurements

The superconducting critical temperature T_c of each sample was measured using a Quantum Design PPMS facility. Measurements of the resistive transition (Fig.1) show that ML exhibits a higher $T_c=15.4$ K than the 250nm Nb substrate layer (Ref, $T_c=8.9$ K) but lower than SL ($T_c = 16.4$ K). T_c values of NbN films, close to the bulk $T_c = 17$ K of NbN, indicate good quality of the films.

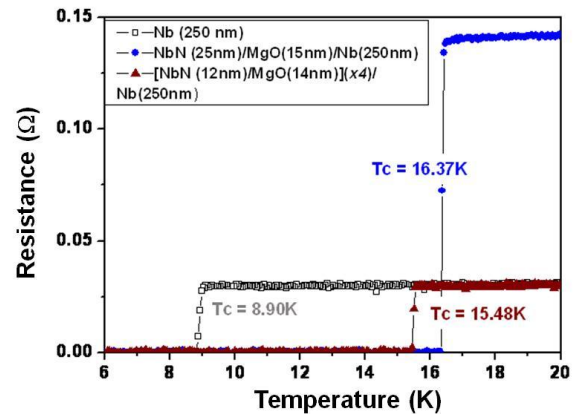


Figure 1: Resistive transition of an Nb film covered or not by a NbN/MgO multilayer

SQUID measurements

Samples for SQUID measurements were cut to 5x5 mm² and glued to high purity quartz wires and aligned either parallel or perpendicular to the magnetic field. DC magnetization curves $M(H)$ parallel to the film surface have been measured using a Quantum Design MPMS equipped with a setup which enables simultaneous measurements of $M(H)$ for both transverse and longitudinal moment orientation. The orthogonal field configuration was also tested.

Note that H_{c1} extracted from DC measurements is lower than H_{c1} at *rf* frequencies Generally H_{c1} (unlike the superheating field) increases as the frequency increases because the vortex does not have enough time to hop over the magnetic surface barrier.

SQUID measurement of thin superconducting films with H parallel to the sample plane is fairly difficult to analyze as has been pointed out in numerous publications (see e.g. [11-22]).

First of all we detected a strong transverse magnetization signal in all the samples, other a wide range of fields, which induced some cross talk in the longitudinal detection loop. The transverse component should not be observed in the film in the Meissner state in a parallel field [16, 17], but with a ratio aspect of 20 000 characteristic of our samples, any small misalignment between the field and the sample surface ($> 0.005^\circ$) will induce a small perpendicular component of the magnetic moment [13]. Due to the large demagnetization factor, this small perpendicular field component is can also cause penetration of vortices perpendicular to the film surface and induce a remnant transverse moment. The purely geometrical origin of this effect has been inferred by

noting that the first penetration field (not shown) extracted by the transversal component is always the same for SL, ML, single Nb or single NbN layer. However, the longitudinal component of the magnetization for the parallel field configuration show a clear enhancement of the first penetration field (see fig. 3), even though only one side of our Nb film was covered with NbN layers.

Signal analysis

If the magnetic barycenter of the sample was perfectly centered on the detection coils symmetry axis, there would be no SQUID response crosstalk between longitudinal and transverse magnetic moment [23]. As this condition is practically impossible to achieve, we have processed the SQUID Raw Data to extract separately the longitudinal and transverse magnetic moment. The commercial fitting procedure is not able to fit properly such a composite signal and we had to develop a proper ad hoc procedure to extract the true longitudinal response.

This procedure was performed in three steps : first we apply a Fourier Transform (FFT) on the SQUID Raw Data in order to separate the symmetric (even) signal from the asymmetric signal (odd). Once the separation of the two signal is done, we perform back an inverse Fourier Transform of the real part of the result. Finally we apply an iterative fit with the appropriate SQUID response equation for each set of coils. This last step is similar to the usual commercial fitting procedure.

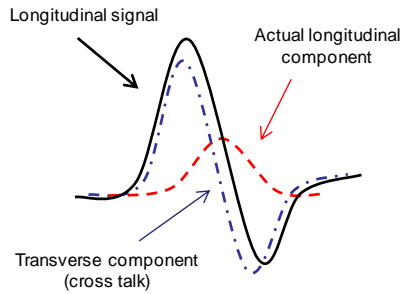


Figure 2: schematic feature of SQUID signals before and after deconvolution.

The paramagnetic signal of the sapphire substrate was measured independently and then subtracted from the data.

Note that qualitative conclusion drawn from the untreated signal (as previously published[24]) are overall not changed, but in fact they reflected only the transverse component. The general feature of the longitudinal moment is now totally changed as it was dominated by the transverse signal cross talk.

For the sake of simplicity, we will only present the results for the reference R and the single NbN layer SL in this section. The multilayer presents the same general features as SL, but with additional instabilities in the first and third quadrant (probably due to vortex jump instabilities during the field change [25, 26]), that will be detailed elsewhere.

Figure 3 shows the longitudinal component of the moment of the reference sample (250 nm Nb) measured at $T=4.5$ K. The first penetration field of about 18 mT for the Nb reference sample is much lower than the $B_{C1} \sim 150$ mT at 4.5K) for clean bulk Nb, but is consistent with the penetration fields of magnetron sputtered films, where values around 10 mT have been observed [27].

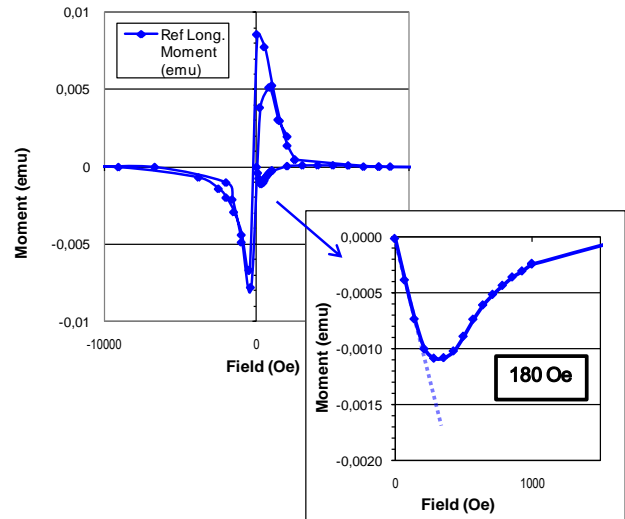


Figure 3 : Magnetization curves at 4.5 K for the reference sample (250 nm Nb): longitudinal moment. Inset shows the determination of the first penetration field B_p . As expected for an isotropic superconductor, B_p is found the same in the transverse direction (not shown here).

Figure 4 shows the magnetization curve for the SL samples (25 nm NbN layer). In this case the longitudinal moment, exhibit a totally different behavior: it has a fishtail shape commonly observed on thin plate type II superconductors [25, 28-30].

The first penetration field in the longitudinal direction is greatly enhanced and reaches 960 Oe, ~ 5 times higher than the reference's one.

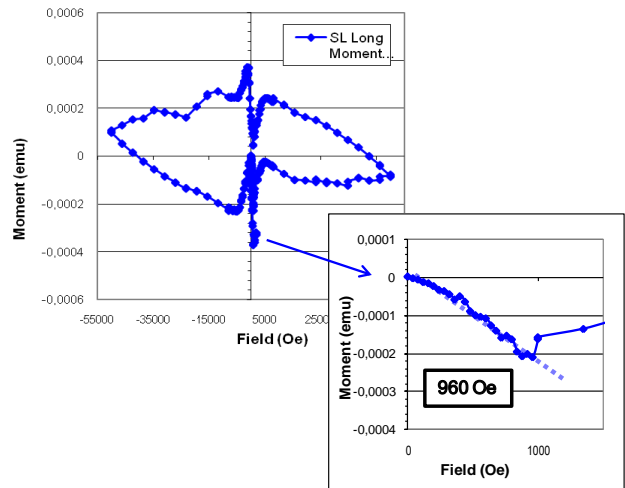


Figure 4: Magnetization curves at 4.5 K for the SL sample (25 nm NbN top layer): longitudinal moment.

Inset shows the determination of the first penetration field B_p .

We have also measured under the same conditions a single (~ 30 nm) layer of NbN deposited on sapphire without Nb underneath. As shown on figure 5, in this case the longitudinal magnetization curve exhibits a first penetration field B_p , about 18 mT. The magnetization curves also exhibit a larger hysteresis (between -5000 and $+5000$ Oe) either in the longitudinal as well in the transverse direction (not shown), which is not observed on the SL layer. This observation and the results presented in the next § support that the enhanced first penetration field observed on SL is related to the whole multilayer structure rather than the thin NbN layer alone. In this case the Nb substrate provides an effective barrier for penetration of perpendicular fortices in NbN film.

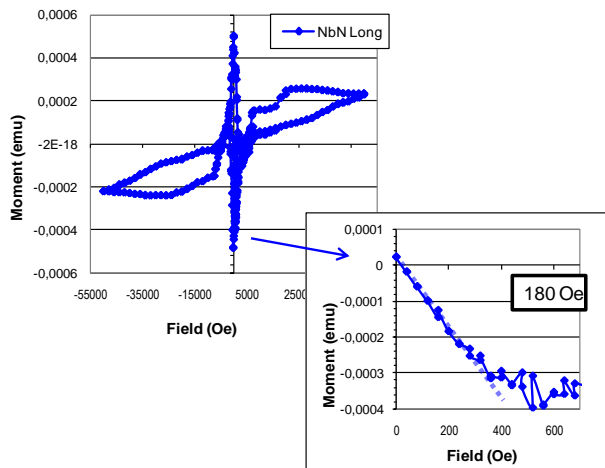


Figure 5: Magnetization curves for a NbN sample (~ 30 nm NbN directly deposited on sapphire): longitudinal moment. Inset shows the determination of the first penetration field B_p .

PERSPECTIVES

3rd harmonic analysis

Since SQUID measurements are strongly influenced by the film orientation, edge and shape effects, we propose to develop a specific local magnetic measurement of H_{C1} based on ac third harmonic analysis as described in ref. [31]. This technique is based on the hysteretic behavior of the magnetization in the critical state, that gives rise to non zero odd harmonics in the spectrum of the electrodynamic response of superconductors exposed to an ac magnetic field. In fig. 4, $V_3(T)$ is strictly equal to zero in the Meissner phase, but it acquires finite values with a bell-shape temperature dependence in the mixed state below the irreversibility line and it comes back to zero in the flux flow and normal state regimes.

First measurement on 80 nm niobium multilayers seems to show a clear increase of B_{C1} in perpendicular field configuration [31]. Likewise, our samples were also measured in perpendicular field. The behavior of the samples SL is clearly different from Nb or NbN alone.

Even in this unfavorable field configuration, it is fairly higher than the reference sample, but only in the temperature range where Niobium too is superconducting. These results will be detailed elsewhere, but they further support the effectiveness of the shielding of niobium in layered structures [32].

In our case we need to develop in addition an experimental set-up where the field configuration is similar to cavities, i.e. parallel to the surface.

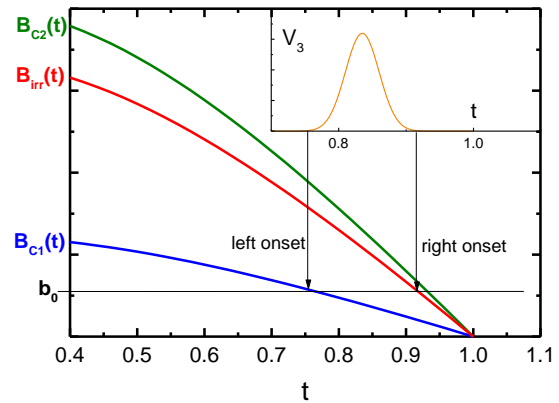


Figure 6: principle of third harmonic analysis (see text for details). $t = T/T_c$

Depositing technique

We need to determine how the screening properties evolve in more realistic situations. We plan to test samples deposited on bulk monocrystalline and polycrystalline niobium with the same technique or with alternative techniques like ALD, which might be easier to develop for full cavity deposition.

CONCLUSION

We have presented the superconducting properties of composite structures specifically designed for *rf* accelerating applications. In particular we have analyzed SL and ML multilayer by DC SQUID magnetization measurement in a parallel field configuration. We have shown a very promising behavior of these composite structures: the first critical field of a multilayer is strongly enhanced and the vortex penetration is prevented at fields higher than the niobium first penetration field when the field is parallel to the surface.

Moreover, when the field is applied locally, this effect seems to be also noticeable in perpendicular field as shown by the 3rd harmonic analysis.

These results are encouraging for cavity application where the non planarity of the surface may induce some local small vertical field component. We must now optimize the number and thickness of layers necessary to reach the best shielding effect. Increasing the number of layer should indeed increase the shielding, but depending on the deposition technique, some degradation

of the layers' quality with thickness is expected, and probably a compromise must be found in more realistic conditions. Various other superconducting materials should also be tested. We need to determine how the screening properties evolve in more realistic situations. We plan to test samples deposited on bulk monocrystalline and polycrystalline niobium with the same technique or with alternative techniques like ALD, which might be easier to develop for full cavity deposition. Ultimately RF cavities should be tested at 1.3 GHz. Recent results obtained on a 20 GHz Nb strip line resonator show that H_{C1} is indeed significantly increased in thin films under RF field [33].

ACKNOWLEDGEMENTS

The research leading to these results has received partial funding from the European Commission under the FP7 Research Infrastructures project EuCARD, grant agreement no. 227579.

REFERENCES

- [1] P. Bauer, et al., "Evidence for non-linear BCS resistance in SRF cavities ". *Physica C*, 2006. **441**: p. 51–56.
- [2] A. Gurevich, "Multiscale mechanisms of SRF breakdown". *Physica C*, 2006. **441**(1-2): p. 38-43
- [3] http://conferences.jlab.org/tfsrf/Tuesday/Tu2_3-Trapped_vortices_Ciovati.pdf
- [4] http://tdserver1.fnal.gov/project/workshops/RF_Materials/talks/A-M_Valente-Feliciano_NewMaterialsOverview.ppt
- [5] A. Gurevich, "Enhancement of RF breakdown field of SC by multilayer coating". *Appl. Phys.Lett.*, 2006. **88**: p. 12511.
- [6] http://conferences.jlab.org/tfsrf/ThinFilmWorkshop_Agenda.pdf
- [7] T. Proslir, et al., "Improvement and protection of niobium surface superconductivity by Atomic Layer Deposition and heat treatment". *APL*, 2008. **93**: p. 192504.
- [8] M.J. Pellin, et al. "Initial tests of atomic layer deposition (ALD) coatings for superconducting RF systems.". in *SRF 2007*. 2007. Beijing, China.
- [9] J-C. Villegier et al, 'Epitaxial growth of sputtered ultra-thin NbN layers and junctions on sapphire', *IEEE trans. on Appl. Supercon.*, 2009, 19, N°3, p. 3375-3378
- [10] L. G. Parratt, "Surface Studies of Solids by Total Reflection of X-Rays", *Phys. Rev.* 95, 359 (1954)
- [11] L. Civale, et al., "Angular-dependent vortex pinning mechanisms in YBaCuO coated conductors and thin films". *Applied Physics Letters*, 2004. **84**: p. 2121.
- [12] D. Feinberg and C. Villard, "Intrinsic pinning and lock-in transition of flux lines in layered type-II superconductors". *Physical review letters*, 1990. **65**(7): p. 919-922.
- [13] C. Monton, F. de La Cruz, and J. Guimpel, "Magnetic behavior of superconductor/ferromagnet superlattices". *Physical Review B*, 2007. **75**(6): p. 64508.
- [14] F.M. Sauerzopf, H.P. Wiesinger, and H.W. Weber, "Anisotropic current flow and demagnetization corrections in the Bean model". *Cryogenics*, 1990. **30**(7): p. 650-655.
- [15] E.M. Gyorgy, et al., "Anisotropic critical currents in BaYCuO analyzed using an extended Bean model". *Applied Physics Letters*, 1989. **55**: p. 283.
- [16] S. Candia and L. Civale, "Angular dependence of the magnetization of isotropic superconductors: which is the vortex direction?". *Superconductor Science and Technology*, 1999. **12**: p. 192-198.
- [17] J.R. Thompson, et al., "Field, temperature, and angle dependent critical current density J_c (H , T , θ) in coated conductors obtained via contact-free methods". *Superconductor Science and Technology*, 2010. **23**: p. 014002.
- [18] E. Zeldov, et al., "Magnetization and transport currents in thin superconducting films". *Physical Review B*, 1994. **49**(14): p. 9802-9822.
- [19] K. Lit and Y. Zhangt, "Enhancement of H_{c1} and its influence on the irreversibility lines in multilayer YBaCu307/PrBaCu307 thin films".
- [20] L.E. De Long, et al., "Extrem magnetic anisotropy and multiple superconducting transition signatures in a [Nb(23nm)/Ni(5 nm)]5 multilayer". *Physica C: Superconductivity and its applications*, 2008. **468**: p. 523-530.
- [21] S. Kryukov, W. Xu, and L. de Long. "A Practical Algorithm for Fitting Magnetic Moment Data for Superconducting Thin Films and Multilayers in Parallel Magnetic Fields". in *APS March Meeting*. 2007.
- [22] A.A. Zhukov, et al., "Geometrical locking of the irreversible magnetic moment to the normal of a thin-plate superconductor". *Physical Review B*, 1997. **56**(5): p. 2809-2819.
- [23] Quantum Design MPMS Application Note 1014-202 A
- [24] C.Z. Antoine, et al. "Characterization of superconducting multilayer samples". in *SRF 2009*. 2009. Berlin, Germany.
- [25] V.V. Chabanenko, et al., "Magnetothermal instabilities in type II superconductors: The influence of magnetic irreversibility". *Journal of Applied Physics*, 2000. **88**: p. 5875.
- [26] A. Nabialek, et al., "Giant magnetostriction and flux jumps in superconducting Nb 3 Al polycrystalline slab". *Journal of Low Temperature Physics*, 2005. **139**(1): p. 239-246.

- [27] N.I. Balalykin and A.B. Kuznetsov, "About the Amplitude Dependence of the Surface Resistance of Niobium Coated Copper Cavities".
- [28] G.P. Mikitik, "Critical states in thin planar type-II superconductors in a perpendicular or inclined magnetic field (Review)". *Low Temperature Physics*. **36**: p. 13.
- [29] R. Lortz, et al., "Origin of the magnetization peak effect in the Nb₃Sn superconductor". *Physical Review B*, 2007. **75**(9): p. 94503.
- [30] L. Krusin-Elbaum, et al., "'Phase diagram' of the vortex-solid phase in Y-Ba-Cu-O crystals: A crossover from single-vortex (1D) to collective (3D) pinning regimes". *Physical review letters*, 1992. **69**(15): p. 2280-2283.
- [31] R. Russo, et al., "Niobium Coating of Cavities using Cathodic Arc". *IEEE Transactions on Applied Superconductivity*, 2009. **19**(3): p. 2682
- [32] To be presented at ASC 2010
- [33] N. Groll, A. Gurevich, and I. Chiorescu, "Measurement of the nonlinear Meissner effect in superconducting Nb films using a resonant microwave cavity: A probe of unconventional pairing symmetries". *Physical Review B*. **81**(2): p. 20504.