

DAPNIA-SEA-96-02

01/1996

Materials for superconducting cavities

# DAPNIA

B. Benin

Le DAPNIA (Département d'Astrophysique, de physique des Particules, de physique Nucléaire et de l'Instrumentation Associée) regroupe les activités du Service d'Astrophysique (SAp), du Département de Physique des Particules Élémentaires (DPhPE) et du Département de Physique Nucléaire (DPhN).

Adresse : DAPNIA, Bâtiment 141  
CEA Saclay  
F -91191 Gif-sur-Yvette Cedex

To be published in CERN Accelerator School.  
Superconductivity in Particle Accelerators,  
**Hambourg**, 16-24/05/95

# MATERIALS FOR SUPERCONDUCTING CAVITIES

*B. Bonin*

Commissariat à l'Energie Atomique, DSM/DAPNIA, France

## Abstract

The ideal material for superconducting cavities should exhibit a high critical temperature, a high critical field, and, above all, a low surface resistance. Unfortunately, these requirements can be conflicting and a compromise has to be found. To date, most superconducting cavities for accelerators are made of niobium. We shall discuss here the reasons for this choice. Thin films of other materials such as NbN, Nb<sub>3</sub>Sn, or even YBCO compounds can also be envisaged and are presently investigated in various laboratories. We show here that their success will depend critically on the crystalline perfection of these films.

## 1. INTRODUCTION

The advantages of superconducting cavities over normal conducting cavities are well known. These advantages can be exploited in many different ways, since they permit continuous operation of the accelerator, improve the energetic conversion to the beam, relax the constraints on cavity design and minimize the cavity impedance seen by the beam. According to the accelerator characteristics, e.g. duty cycle, intensity, beam dynamics properties, a different priority is given to each of these advantages. Nevertheless, it should be remembered that all the advantages of superconducting cavities stem from one single property of the superconducting material, namely its very low surface resistance. We shall discuss first the requirements imposed on the superconductor by this criterion of minimal surface resistance.

## 2. CRITERIA OF CHOICE DERIVED FROM THE SURFACE RESISTANCE

The power dissipation per unit area of a superconductor in RF regime is related to the surface resistance of the material  $R_S$  via :

$$P = \frac{1}{2} \cdot R_S \cdot H^2 \quad (1),$$

where  $H$  is the RF magnetic field amplitude. A well known expression for the surface resistance of a superconductor can be derived from the two fluid model [1]:

$$R_S = \frac{A}{T} \cdot \sigma_n \cdot \omega^2 \cdot \lambda^3 \cdot e^{-B \cdot T_c / T} + R_{\text{residual}} \quad (2),$$

where  $A$  and  $B$  are two constants which depend only weakly on the material,  $\omega$  is the RF pulsation,  $\sigma_n$  the normal state conductivity of the material,  $\lambda$  its effective penetration depth, and  $T_c$  the superconductor critical temperature. The first term, improperly called  $R_{BCS}$ , corresponds to the dissipation due to normal electrons, and the second,  $R_{\text{residual}}$ , is associated with imperfections in the superconductor structure and behaviour.

In many practical cases, the BCS term takes a non negligible fraction of the total surface resistance. As can be seen from eq. 2,  $R_{BCS}$  depends strongly on the superconductor penetration depth and critical temperature. It is thus crucial to maximize  $T_c$  (requirement 1) and to minimize  $\lambda$  (requirement 2).

In eq. 2, the penetration depth  $\lambda$  is an effective value, related to the London superconductor penetration depth  $\lambda_L$  by  $\lambda = \lambda_L \cdot \sqrt{\frac{\xi_0}{\xi}}$ , where  $\xi_0$  and  $\xi$  are the coherence lengths in the pure and real material respectively. In the real material, the coherence length is given by

$$\xi^{-1} = \xi_0^{-1} + l^{-1},$$

where  $l$  is the electron mean free path. Two extreme cases can then be envisaged :

For clean superconductors, i.e those with a large electron mean free path,  $l \gg \xi_0$ , thus  $\xi \approx \xi_0$ , and eq. 2 gives  $R_{BCS}^{clean} \propto l$ . For very clean material, eq. 2 is no longer valid, and more sophisticated calculations based on BCS theory [2] predict a roughly constant surface resistance, independent of  $l$ , and thus, of the material purity.

For dirty superconductors, i.e those with a small electron mean free path,  $l \ll \xi_0$ , thus  $\xi \approx l$ , hence  $R_{BCS}^{dirty} \propto l^{-1/2}$ . The surface resistance thus diverges for very dirty superconductors (fig.1).

Between the clean and dirty limits,  $R_{BCS}$  takes a minimum value when the electron mean free path becomes comparable to the coherence length.

Pure metals and pure intermetallic compounds with a well defined stoichiometric composition, like Nb<sub>3</sub>Sn, are usually clean superconductors, except if they are elaborated with many crystalline defects; on the other hand, alloys enter the category of dirty superconductors, due to their very small electron mean free path. Consequently, they display large BCS surface resistance. For the same reason, i.e a small electron mean free path, alloys also have a poor thermal conductivity at cryogenic temperatures, thus hampering the thermal stability of a cavity. For these two reasons, alloys are not suitable materials for superconducting cavities.

BCS Surface resistance vs e<sup>-</sup> mean free path

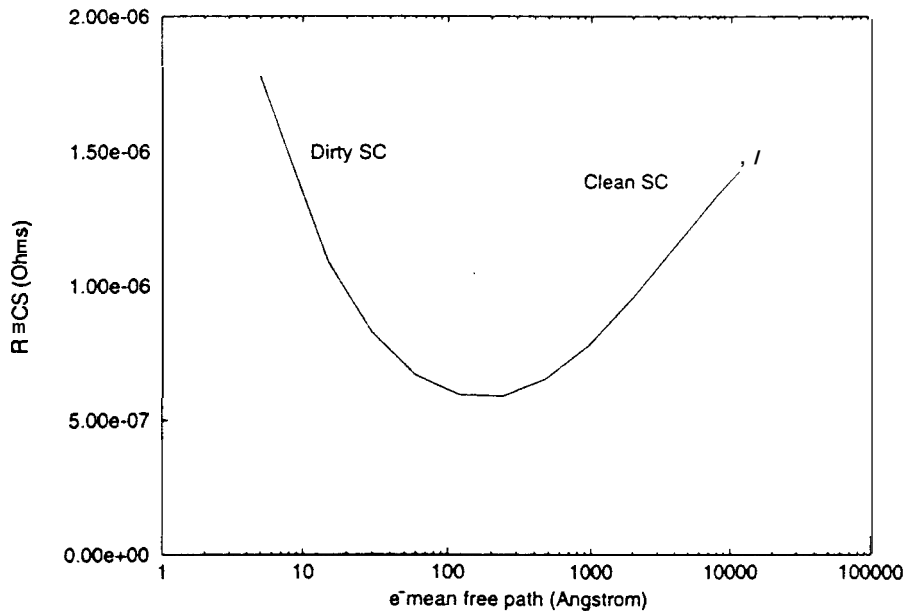


Fig. 1 The BCS surface resistance of Niobium at 1.5 GHz and 4.2 K, as a function of the electron mean free path.

Usually, the optimum working conditions of the superconducting cavity are met when  $R_{BCS} \approx R_{residual}$ . It is therefore very important to minimize this last term. Many causes contribute to the residual surface resistance [3]. Some of these are extrinsic (trapped flux), and can be avoided. Some causes are intrinsic and are due to structural imperfections of the material, like inhomogeneities, grain boundaries or surface serration. The superconducting wave function or order parameter is sensitive to defects larger or of the same size as the coherence length  $\xi$  [4]. Materials with a large  $\xi$ -value will thus “forgive” large defects without an appreciable increase of the residual surface resistance. This is clearly a desirable feature for cavity applications, where square meters of superconducting surface are exposed to the RF field, and are presumably difficult to prepare completely “defect-free”.

Putting requirements 2 (small penetration depth) and 3 (large coherence length) together, we get the description of a type I superconductor. These are universally known as low  $T_c$  superconductors, and this is clearly in contradiction with requirement 1. The BCS theory [2] gives a relationship between the coherence length and the critical temperature :

$$\xi_0 = 0.18 \frac{\hbar v_F}{k T_c}, \text{ where } v_F \text{ is the Fermi velocity. The inverse relationship between the}$$

coherence length and the critical temperature indicates that the contradiction between requirements 1 and 3 is very deep indeed. Therefore, the ideal superconductor for RF applications does not exist, and subsequent choices clearly result from a compromise.

Lead, as an archetype of a type I superconductor, has been used for low frequency cavities, and has yielded a very low residual surface resistance. It is cheap, and easily available in a pure form. Unfortunately, at frequencies higher than a few hundred MHz, the BCS surface resistance becomes prohibitive, due to the low critical temperature of this material. Moreover, it has poor mechanical characteristics and oxidizes easily, with a subsequent degradation of the properties of the superconducting surface. For these reasons, Lead tends to be progressively replaced by Niobium, and is now confined to low frequency applications.

Type II superconductors can have a large  $T_c$  and a reasonably small penetration depth, so that their BCS surface resistance can be small, even at rather high cryogenic temperature. But their coherence length  $\xi$  is small, so type II superconductors tend to display rather high residual surface resistance, unless they are prepared “defect-free” (fig. 2).

Table 1 summarizes the characteristics of various superconductors :

	$T_c$ (K)	$\lambda$ (nm)	$\xi_0$ (nm)
Pb	7.2	39	83-92
TYPE I ↑		---	---
TYPE II ↓			
Nb	9.2	32-44	30-60
Nb <sub>0.6</sub> Ti <sub>0.4</sub>	9.8	250-320	4
NbN	15-17	200-350	3-5
Nb <sub>3</sub> Sn	18	110-170	3-6
YBCO	94	140	0.2- 1.5

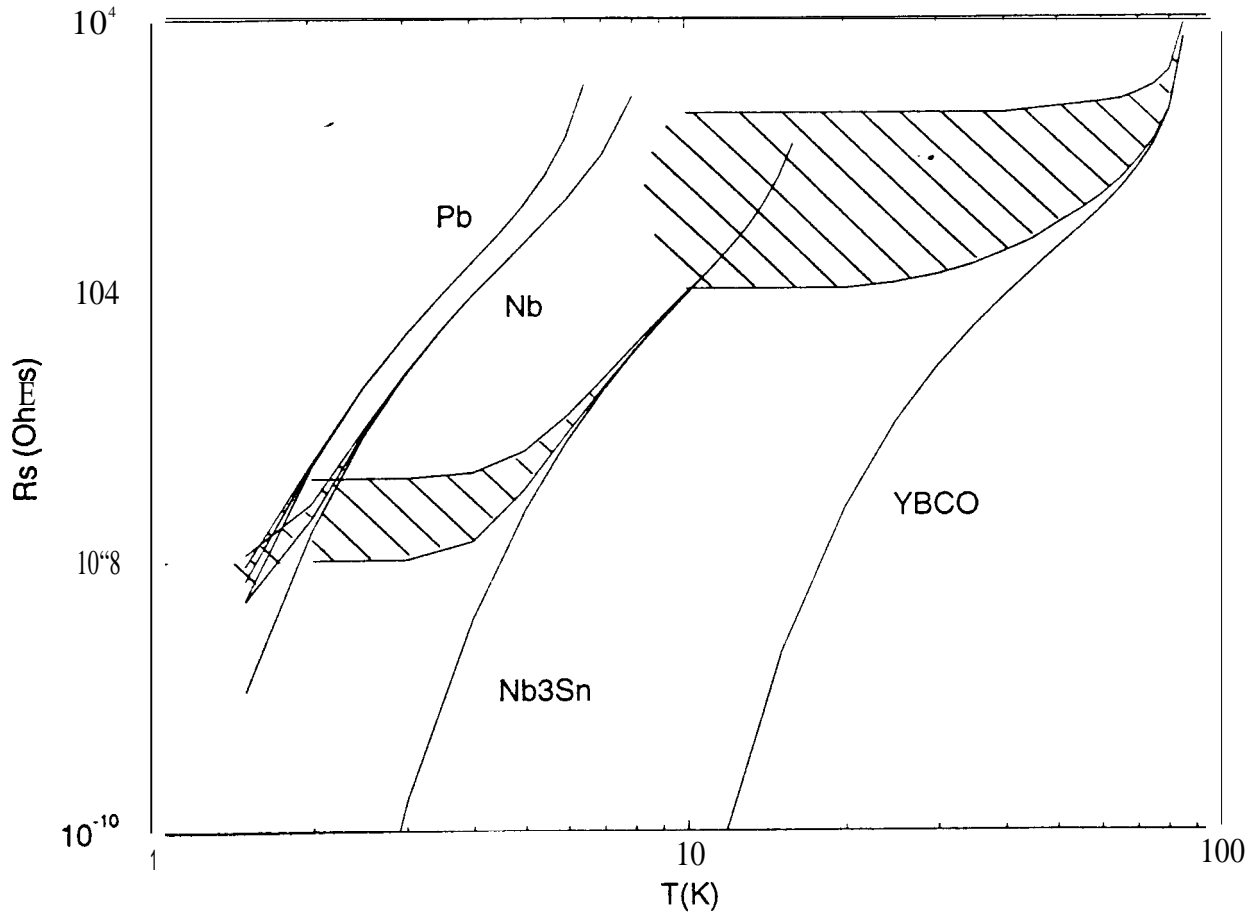


Fig.2 The surface resistance vs temperature for a few typical superconductors at 1.5 GHz. In this picture, the full lines show the BCS contribution, and the hatched areas represent the total surface resistance for "state of the art" materials.

### 3. CRITICAL FIELD

High magnetic fields are present in accelerating cavities. In many cases, the amplitude of the RF magnetic fields approaches the order of magnitude of the superconductor critical fields. A superconducting material with a high critical field is thus desirable for RF applications (requirement 4). Since the nucleation time of a vortex is usually large as compared with the RF period, the relevant critical field of an RF superconductor is not the usual critical fields  $H_{C1}$  or  $H_{C2}$ , but is believed to be the superheating field  $H_{Sh}$  [5].  $H_{Sh}$  is related to the thermodynamic critical field  $H_{th}$  via :

$$H_{sh} = 0.89 \cdot \frac{H_{th}}{\sqrt{\kappa}} \quad \kappa \ll 1$$

$$H_{sh} \approx H_{th} \quad \kappa \gg 1$$

It should be noted that for type II superconductors,  $H_{Sh}$  can be significantly larger than  $H_{C1}$ .

Theoretical arguments in favor of the hypothesis that the limiting RF field is  $H_{Sh}$  are supported by the fact that experimentally, the superheating limit has been approached, but never broken [6].

Table 2 gives the thermodynamic field, superheating field and maximum attained RF field for various superconductors.

	H <sub>th</sub> (A/m)	H <sub>sh</sub> (A/m)	H <sub>RF</sub> max (A/m)
Pb	6.4 10 <sup>4</sup>	8.4 10 <sup>4</sup>	6.4 10 <sup>4</sup>
Nb	1.6 10 <sup>5</sup>	1.9 10 <sup>5</sup>	1.6 10 <sup>5</sup>
Nb <sub>3</sub> Sn	2.5 10 <sup>5</sup>	3.2 10 <sup>5</sup>	8.0 10 <sup>4</sup>
YBCO	≈ 6 10 <sup>5</sup> - 10 <sup>6</sup>	≈ 6 10 <sup>5</sup> - 8 10 <sup>5</sup>	8.0 10 <sup>4</sup>

#### 4. NIOBIUM

In view of the above criteria, Nb appears as a serious candidate for superconducting cavities. It has the highest T<sub>C</sub> and H<sub>sh</sub> of all pure metals. Being a soft type II superconductor, it occupies a position of compromise between the four requirements mentioned above.

Niobium homogeneity and purity are important issues for RF applications because it determines the thermal stability of the cavity. It was realized early that a frequent gradient limitation in superconducting cavities is due to thermal instabilities triggered by microscopic hot spots, for example normal conducting inclusions. This led researchers to investigate in detail the thermal behaviour of niobium cavities, in relation with the material characteristics [7].

##### Niobium thermal conductivity

Two parameters are relevant for the description of the thermal behaviour of the cavity, namely the niobium thermal conductivity and the Kapitza resistance at the niobium-helium interface. In the case of a hot spot, most of the thermal gradient is located in the niobium sheet, and the thermal properties of the interface play a minor role [7]. For a good thermal stability, a niobium cavity must thus be made from a material with high thermal conductivity. At cryogenic temperatures, the main heat carriers in niobium are electrons, and their mean free path is limited primarily by collisions with impurity atoms [8].

The electron mean free path is usually given in terms of a quantity (residual resistivity ratio), defined as :

$$RRR = \frac{\rho_{300K}}{\rho_{0K}}$$

where  $\rho_{300K}$  is the room temperature resistivity (this term is constant,  $\rho_{300K} = 1.45 \cdot 10^{-7} \Omega^{-1} \cdot m^{-1}$ ) and  $\rho_{0K}$  the normal state resistivity of niobium at zero temperature.

The approximate relationship giving the electron mean free path in niobium as a function of RRR is :

$$l(T = 0K)(\text{Angstrom}) \approx 27 \cdot RRR.$$

The thermal conductivity of niobium (fig. 3) has been parametrized as a function of purity and past metallurgical history. A useful rule of thumb is :

$$\lambda(T = 4.2K)(W \cdot m^{-1} \cdot K^{-1}) \approx RRR / 4.$$

With usual values of RRR (a few hundreds), this relationship gives a thermal conductivity significantly smaller for niobium than for OFHC copper.

In the superconducting state, paired electrons in niobium decouple from the lattice and no longer participate in heat conduction. Heat is then carried by the small fraction of unpaired electrons. The poor thermal conductivity of niobium is thus intrinsically due to its superconducting nature. Altogether, a Nb layer of 1 $\mu$ m thickness would be sufficient for superconducting cavities. Expensive as it is, the rest of the material serves merely as a substrate, despite its poor mechanical and thermal properties!

The above arguments show how important it is to make superconducting cavities with very pure material. One of the most significant advances in cavity **performance** is due to a recent effort **from** niobium suppliers to produce niobium of improved purity.

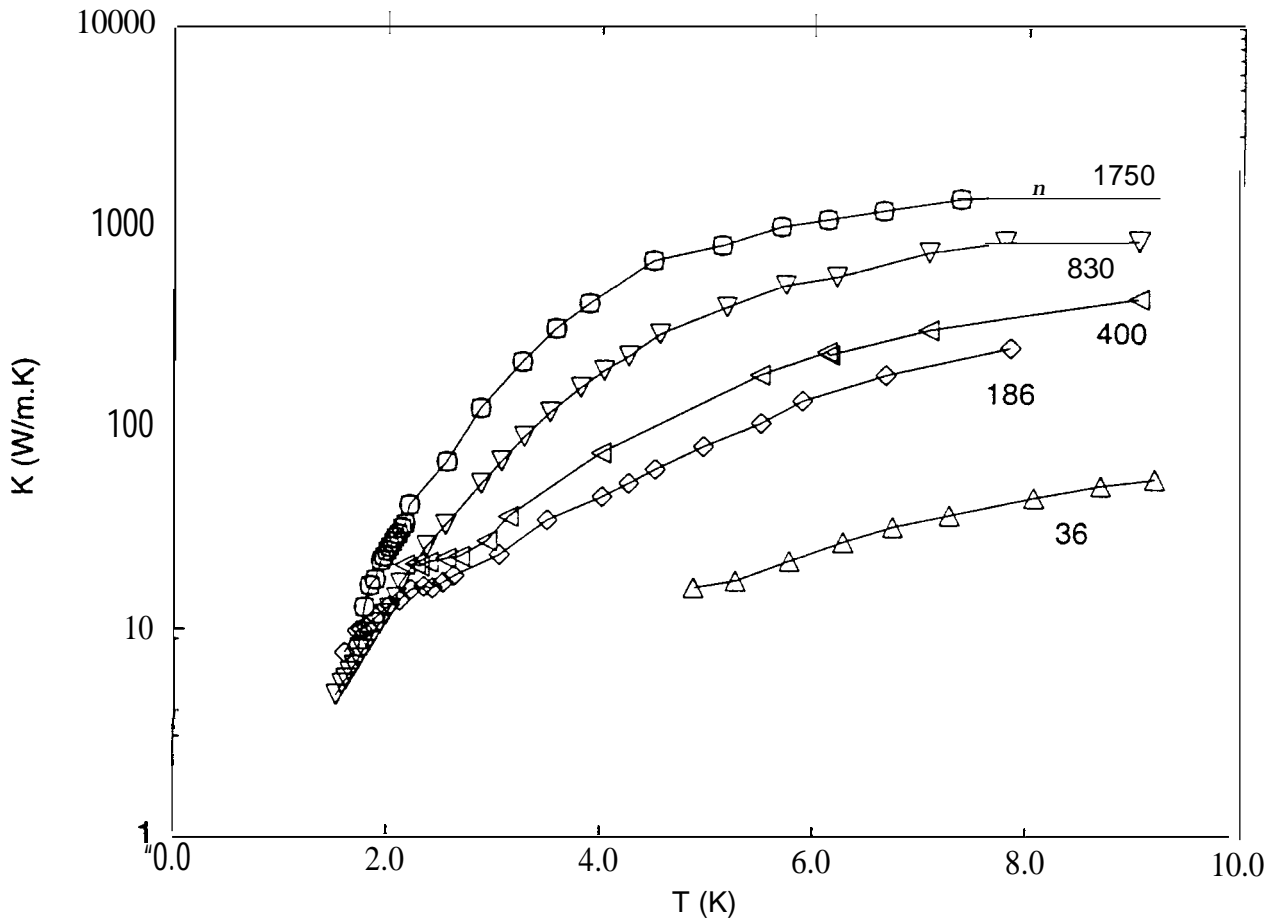


Fig. 3 The thermal conductivity of niobium as a function of temperature, for various **RRR** values.

#### Niobium elaboration

Niobium elaboration from the ore to the raw ingot involves a complicated path, with chemical treatments and high temperature steps, which have been **described** in [9].

The purified ingot is then **rolled** in sheet form. Recrystallization annealing are usually performed by the supplier, between the rolling steps or before the sheet delivery, in order to warrant a uniform and well controlled grain size (typically  $50\mu\text{m}$ , for good sheet deformation capabilities). The cavity can then be **formed**.

The main impurities which contribute to the **RRR** degradation are **C,N,O** [9]. For **state-of-the-art** material (**RRR** 300), these are present with a concentration of about 100 at. **ppm**; Tantalum is also present in large amounts (1000 at. **ppm**). This element is difficult to separate from niobium because both have very similar **chemical** properties.



Niobium purity is improved by electron beam melting (2400°C) in high vacuum. Light impurities (C,N,O,H) are vaporized during the process; four to six passes are generally considered to be necessary to reach a RRR level of the order of 300 [9].

### **Niobium postpurification**

Postpurification of niobium can be achieved by a heat treatment associated with solid state gettering [10]. The material, either in sheet or in finished cavity form, is heated under high vacuum at temperatures ranging between 1000°C and 1400°C. This temperature is sufficient to permit diffusion of interstitial impurities C,N,O in the bulk material. The material is thus homogenized, thanks to the dissolution of the inclusions. At the same time, a liner of titanium placed close to the material to be purified sublimates. Its vapor deposits at the niobium surface and acts as a getter for the interstitial impurities which diffuse here. After a few hours of heat treatment, the bulk niobium can be purified to a large extent. This technique is now capable of improving the niobium RRR by a factor of 10 (from 30 to 300 for "reactor grade" material, and from 200 to 2000 for "state of the art" material). Niobium thermal conductivity can be considerably improved by this treatment, with a subsequent improvement of the cavity quench threshold. In spite of its drawbacks (cost, severe degradation of the material mechanical properties), niobium postpurification is presently an interesting road for obtaining very high cavity performance.

## **5. THIN FILMS**

Fabrication of superconducting cavities by deposition of a thin superconducting film can also be envisaged. For a complete screening of the RF field by the superconductor, a minimum thickness of 10 times the penetration depth  $\lambda$  should be deposited. This corresponds to a thickness ranging between 0.5 and 2  $\mu\text{m}$ . This thickness domain is accessible to many deposition techniques. Considerable advantages can be expected from such "thin film" cavities:

- a cheap substrate can be used, with a subsequent cavity cost saving;
- a good heat conductor can be chosen for the substrate, giving a good cavity thermal stability.

These two criteria can be met by use of copper as a substrate.

- materials unavailable in bulk form can be deposited in thin films, with potentially interesting superconducting properties.

### **Nb/Cu thin films**

A number of superconducting materials have been investigated for RF applications. So far, the most successful is niobium, sputter-deposited on a copper substrate. The deposition method, pioneered at CERN [11], is DC magnetron sputtering. Here, the copper cavity plays the combined roles of substrate and vacuum vessel, and the niobium target (cathode) is introduced at the center of the vessel. The method is well suited to large cavities, working at low frequency, and at 4.2 K. In this case, it provides an appreciable cost saving in supply material. In addition, the RRR of the deposited material is around 30, close to the optimum value which minimizes the BCS contribution to the surface resistance. The archetype of this kind of application is LEP2 cavities. After a difficult start, this technology has now been transferred to industry, which provides cavities meeting the LEP2 specifications with a good success rate.

### **Nb(Ti)N thin films**

Deposition of niobium nitride films has also been attempted in various laboratories[12]. Here, the hope is to exploit the high critical temperature of this intermetallic compound (17 K) to lower the BCS contribution to the surface resistance, and to permit cavity operation at temperatures higher than 2 K (the goal is 4.2 K). The deposition method used so far is reactive

sputtering, with a pure metallic target of Nb or NbTi alloy, and introduction of nitrogen in the sputtering gas.

So far, full success cannot be claimed. Only encouraging results have been obtained on samples, with low surface resistance at low field levels (400 m $\Omega$  at 4 GHz), and a BCS contribution much lower than for niobium (three times less at 4.2 K). Nitride accelerating cavities with competitive characteristics have not yet been produced.

### **Nb<sub>3</sub>Sn layers**

Thin films of Nb<sub>3</sub>Sn have had more success (accelerating gradients as high as 15 MV/m, cavity Q-value higher than 10<sup>10</sup> at low fields) [13], but the fabrication method (start from a pure niobium cavity, evaporate tin on its surface, and heat up until Nb<sub>3</sub>Sn is formed on a few  $\mu$ m thickness) is probably expensive and does not lend itself to an easy industrialization. It might be interesting, however, in cases where cost is not a very important criterion, or to upgrade the performance of existing cavities.

### **YBCO**

Theoretically, very low surface resistance could be expected from high T<sub>c</sub> superconductors like YBCO. So far, the experimental results fall short of these expectations [14]. Sintered ceramics display a very large residual resistance. Moreover, R<sub>res</sub> increases dramatically with increasing RF field. Thick coatings prepared by laser ablation, sputtering or other deposition techniques also display more or less the same behaviour, whose cause can be found in the granular nature of the material. Epitaxially grown thin films have much smaller surface resistance, and their surface resistance is independent of the amplitude of the RF field. Their superconducting characteristics could make them attractive for accelerator applications. Unfortunately, they require a monocrystalline substrate, and have been produced until now on flat samples of very restricted area.

### **Granular superconductivity**

Most of the high T<sub>c</sub> superconductor films and all the sputtered films have in common a very unfortunate feature: they display an increase of surface resistance with increasing RF field. This behaviour limits severely the accelerating gradient obtainable from "thin film" or "high T<sub>c</sub>" cavities. The disease seems to be worse for materials with higher T<sub>c</sub>, or, more precisely, with smaller coherence length. The cause of this misfortune can be traced back to the granular nature of this kind of superconducting materials. The RF dissipation of granular superconductors has been investigated by many authors [15]. Here, the superconductor is modelled as an array of superconducting grains separated by weak links which, in the present case, can be structure defects like grain boundaries. The granularity is more pronounced if the grains are smaller, the boundaries more resistive or the coherence length smaller. If the current induced by the RF field through the weak link stays below its critical current, the weak link behaves as a resistively shunted inductance; in the opposite case, the weak link can be modelled as a pure resistor and the power dissipation of the array rises abruptly. These models provide guidelines to produce better, less granular superconducting films. They indicate that a weak link is a defect as large or larger than the coherence length. Since  $\xi_0$  is small for high T<sub>c</sub> materials, the challenge is to make very perfect films, with a minimum number of structure defects.

## **6. CONCLUSION**

In view of the discussed arguments, one can understand why superconductors for magnet applications and superconductors for cavities are so different. The only requirement they have in common is a high critical temperature. Whereas superconductors for magnets need a high H<sub>c2</sub>, and thus a small coherence length, materials for cavities need a low surface resistance and a large superheating field H<sub>sh</sub>. In order to ensure an effective flux pinning, the former needs to be a dirty superconductor, the latter a clean one.

Table 3 summarizes the requirements put on superconducting materials for RF and DC applications.

	$H_c$	$H_{c2}$	$j_c$	$R_s$	$T_c$	$\xi$	$\lambda$	
DC	-	large	large	-	high	small (pinning is needed)	large (bulk current)	NbTi, Nb3Sn
RF	large	-	-	small	high ( $R_s$ depends on $T/T_c$ )	large (to give little sensitivity to structure defects)	small $R_s \propto \lambda^3$	Nb Nb(Ti)N? Nb3Sn? YBCO?
.....								
Primary requirements								
.....								
Consequences								

Altogether, Niobium seems to be an excellent compromise between the conflicting requirements imposed on a superconductor suitable for RF cavities, and its supremacy will probably last long. In view of their superior critical fields and temperatures, compounds like NbN, Nb3Sn or even YBCO are attractive substitutes to niobium, but it will be necessary to elaborate them in a very pure and perfect way in order to avoid problems related with the low coherence length of these materials.

## REFERENCES “

- [1] H. Piel, “Superconductivity in Particle Accelerators”, CERN Course, Hamburg, ed. S. Turner (1988)  
J. H. Hinken, “Superconducting electronics”, Springer Verlag
- [2] C. C. Mattis and J. Bardeen, *Phys. Rev.* 111 412 (1958)
- [3] J. Pierce, “Superconducting microwave resonators” in “Methods of Experimental Physics” vol. 2, ed. R. Coleman, Acad. Press, N. Y. (1974)  
M. Tigner and H. Padamsee in “Physics of high energy particle accelerators”, SLAC summer school (1982), ed. M. Month, *AIP Conf. Proc.* 105, 801 (1983)  
J. Halbritter, *J. Appl. Phys.* 42 82 (1971)  
P. Kneisel, O. Stolz, J. Halbritter, *Proc. of the Appl. Superc. Conf. IEEE*, New York (1972) p 657
- [4] P. Schmüser, this course
- [5] T. Yogi and M. Mercereau, *Phys. Rev. Lett.* 39 826 (1977)  
J. Halbritter, 1st Workshop on RF Superconductivity, Karlsruhe, KfK 3019 (1980)
- [6] W. Weingarten, *Particle World* 1 93 (1990)  
G. Müller, *Proc. 3rd Workshop on RF Superconductivity*, Argonne (1987) ANL-PHY-88-1 p 331
- [7] H. Padamsee, 1st Workshop on RF Superconductivity, Karlsruhe, KfK 3019 (1980)  
H. Padamsee, *IEEE T. Mag.* 19 1322 (1983)
- [8] K.K Schulze, *Journal of Metals*, May 1981, p33
- [9] M. Hörmann, *J. of Less Common Metals* 139 1 (1988)
- [10] T. Haas, *Surf. Sci.* 5 345 (1966)  
E. Fromm, *Vacuum* 19 191 (1969)  
H. Farrell, *Surf. Sci.* 38 31 (1973)
- [11] G. Arnolds-Mayer and W. Weingarten, *IEEE T. Mag.* 23 1620 (1987)  
C. Benvenuti et al., *IEEE T. Mag.* 21 153 (1985)
- [12] C. Benvenuti et al., 5th Workshop on RF Superconductivity, DESY, Hamburg, ed. D. Proch, pp 189 and 518 (1991)  
R. di Leo, A. Nigro, G. Nobile and R. Vaglio, *J. Low Temp. Phys.* 7841 (1990)  
P. Bosland et al, 6th Workshop on RF Superconductivity, CEBAF, USA, ed. R. Sundelin, (1993) p. 1028

- [13] J. J. Hanak et al. RCA Rev. 25342 (1964)
- M. Peiniger and H. Piel, IEEE T. NS 32 3612 (1985)
- R. Roth and P. Kneisel, 7th Workshop on RF Superconductivity, Gif sur Yvette, ed. B. Benin (1995)
- [14] G. Müller, this CERN course.
- [15] L. Cohen, I. R. Gray, A. Porch and J. R. Waldram, J. Phys. F: Metals Physics, 17 L179 (1987)
- A. M. Portis, IEEE T. Mag. 25 2390 (1989)
- O. G. Vendyk et al., Zh. Tekh. Fiz. 59 107 (1989)
- B. Benin and H. Safa, Superc. Sci. Technol. 4 257 (1991)
- C. Attanasio, L. Maritato and R. Vaglio, Phys. Rev. B 43 6128 (1991)